

UNDERSTANDING ANODE OVERPOTENTIAL

Rebecca Jayne Thorne¹, Camilla Sommerse¹, Ann Mari Svensson¹, Espen Sandnes², Lorentz Petter Lossius², Hogne Linga², and Arne Petter Ratvik¹

¹Dept. of Materials Science and Engineering, Norwegian University of Science and Technology, NO-7491 Trondheim, Norway
²Hydro Aluminium, Årdal, Norway

Keywords: Anode, carbon, electrochemistry, characterisation, overpotential.

Abstract

In aluminium electrolysis cells the anodic process is associated with a substantial overpotential. Industrial carbon anodes are produced from coke materials, but the effect of coke type on anodic overpotential has not been well studied. In this work, lab-scale anodes were fabricated from single source cokes and electrochemical methods were used to determine the overpotential of the anode materials. Attempts were then made to explain these trends in terms of both the physical and chemical characteristics of the baked anodes themselves and their raw materials. Routine coke and anode characterisation methods were used to measure properties such as impurity concentrations and reactivity (to air and CO₂), while non-routine characterisation methods were applied to study surface and structural properties. It was found that the overpotential trend of the anodes correlated well with many of the properties studied, and explanations for these observed correlations are suggested. These findings offer exciting possibilities for reducing the energy demand of the anodic process.

Introduction

The overall potential of a typical industrial aluminium cell is around 4.6 V [1]. The total voltage associated with the anode is around 1.5-1.8, referred to the aluminium potential, of which 0.3-0.6 V is the overpotential [1]. Anodic overpotential is composed of three parts – reaction overpotential, concentration overpotential and bubble overpotential (or resistance). Concentration overpotential is thought to be very low at normal current densities, so the overpotential under normal operational conditions mainly comprises of reaction and bubble overpotential [1]. Reducing these components is consequently desirable to decrease the energy demand and production cost of aluminium.

Although the magnitude of anode overpotential has been studied in various melt and set-up conditions, few detailed studies of the relationship of overpotential to anode material properties (chemical and physical) have been performed. Electrocatalysts such as iron, vanadium and calcium have been found both to increase air and CO₂ reactivity [2-5] and cause increased electrolytic anode consumption and/or decreased overpotential [1, 4, 6-8]. However, electrocatalyst studies have mostly focused on artificially doped anode materials which do not necessarily reflect the real situation found in cokes and anodes. Looking at this from the other side, various papers have investigated how changes in physical coke properties, such as structure and density, have

affected anode performance, but have not linked these coke properties to overpotential directly [2, 9-11]. It is likely that coke and anode physical properties will have an effect on overpotential, as the reactivity of carbons, both for electrochemical reactions and oxidation reactions, is generally known to be related to microstructural parameters [12, 13]. In addition, the formation and release of CO₂ bubbles also relies on the surface microstructure [14].

In a previous study that served as preliminary work on a new project, the total overpotential of a range of carbon anodes varying only in coke type was measured [15]. These anodes were labeled 1 to 4, and a distinct overpotential trend was found with anode 4 having a lower overpotential than anode 1 by approximately 200 mV at 1 A cm⁻². The overpotential was found to correlate well with the concentration of metal impurities (electrocatalysts) and total sulphur in the anode, but relationships with other anode properties were not studied. As unshielded rods were used as the anode design (which were immersed in the melt approximately 1.5 cm), other limitations of the initial study included the fact that the immersed anode area was not precisely defined, the current density was not equal over the active anode surface and bubbles trapped underneath the anode could create noise in the electrochemical measurements and generate extra bubble resistance. This paper follows up and expands on the previous study, studying the overpotential of the same series of anode materials. The method with which to study overpotential was improved and further efforts were made to understand the differences in overpotential observed. Correlations of overpotential with some of the main industrial methods traditionally used to characterise anodes (air and CO₂ reactivity) were also investigated.

Materials and Methods

Four types of single source cokes were used to produce pilot scale anodes with a grain size limited to 0-2 mm (the fractions were 2-1, 1-0 and mill product); these were labeled anodes 1 to 4. The production of the anodes varied only in the coke type, all other parameters were kept constant. A graphite material was also tested for a comparison with the industrial quality anodes. For electrochemical measurements, anodes were cut and assembled as schematically depicted in Figure 1. Immersed anode area was defined using boron nitride (BN) shielding. Thus, advantages over the previous anode design (from [15]) included a defined surface area to be immersed in the melt (1.5 cm²), an even current distribution and a minimised bubble retention due to the vertical

surface. The impact of anode geometry was directly compared by also including an unshielded graphite rod in the measurement series, as used in [15]. This is shown in figure 2.

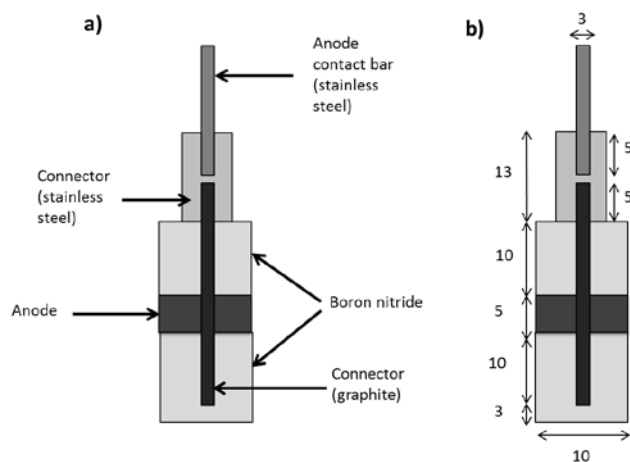


Figure 1. The anode assembly used in this study. All materials were threaded together on a 3 mm graphite rod, which was attached via a connector piece to a stainless steel contact bar. The BN shields defined an active anode surface area of 1.6 cm^2 . Figure 2b. Dimensions of the anode assembly (mm).

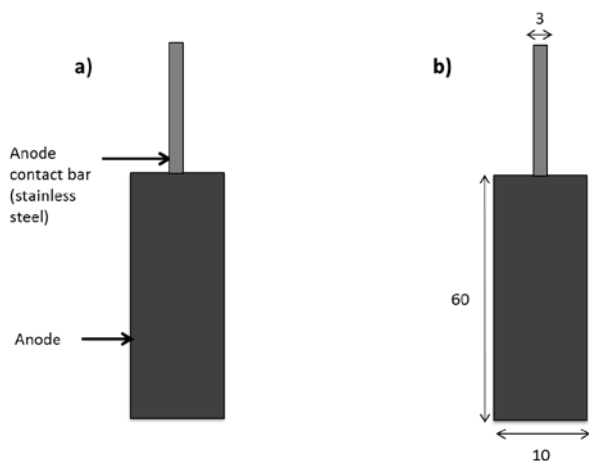


Figure 2. The anode assembly used in [15], which was also used in this study to investigate the impact of anode geometry on electrochemical measurements (i.e. the effect of a horizontal surface). When immersed 1.5 cm in the melt, this had an approximate active anode surface area of 5.5 cm^2 . Figure 2b. Dimensions of the anode assembly (mm).

Experiments were performed in a cryolite melt (cryolite ratio = 2.3 (cryolite from Sigma Aldrich, purity >97 %), with excess AlF_3 equal to 9.8 wt% (industrial grade AlF_3 sublimed in-house) and an alumina concentration of 9.4 wt%, (γ alumina from Merck). The melt was contained in a graphite crucible (Svensk Specialgrafit AB, Sweden) in which an alumina disk was placed. An aluminium reference electrode in an alumina assembly was fabricated according to [16]. A schematic of the overall experimental setup is shown in Figure 3.

All electrochemistry was performed using a Zahner IM6 (with built in EIS module and 10 A booster PP201, all from Zahner-Elektrik). Electrochemical Impedance Spectroscopy (EIS) was used to determine the ohmic resistance at the Open Circuit Potential (OCP), the value of which was used to iR compensate all electrochemical measurements. A current density (CD) of 1 A cm^{-2} was then applied to each anode and the potential measured (relative to an aluminium reference electrode) for 200 seconds, before repeating. This CD of 1 A cm^{-2} was chosen as it is close to the anode CD in modern industrial cells. Polarisation curves were also recorded for each anode by slowly sweeping the anode potential from the OCP to 2.5 V at 0.1 V s^{-1} and measuring the responding current.

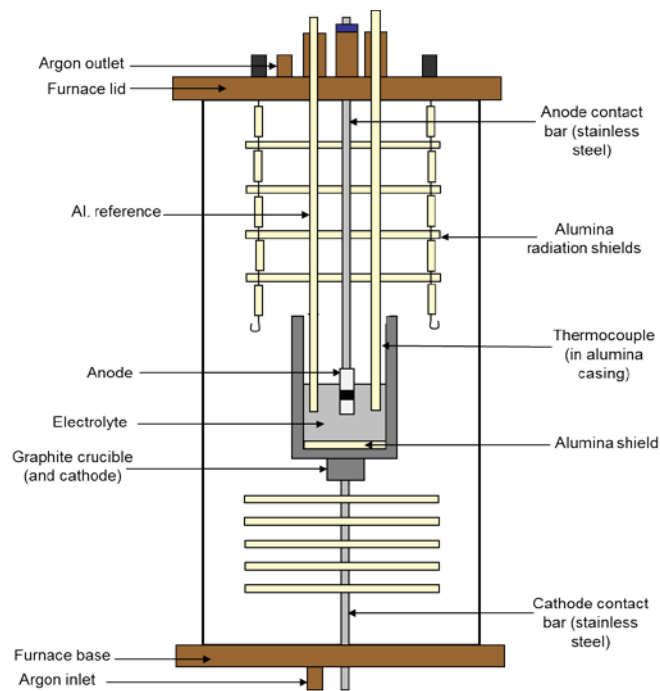


Figure 3. The furnace and crucible setup.

The order of the anode materials tested was randomised to eliminate possible changing characteristics of the melt over time, and two parallels were performed for each material (with new anodes) in the same bath. Bath samples after each anode experiment were taken for subsequent oxide content by combustion analysis (LECO analyser model TC-436DR).

Anode materials were additionally characterised according to routine industrial methods (including air and CO_2 reactivity), and additionally for structure. Isotropy of the anodes was studied using optical microscopy (under polarised light) after mounting anodes in epoxy and polishing to $1 \mu\text{m}$. To further study the relative amount of surface active sites, the oxygen content of the samples was measured using LECO analysis between room temperature and 2800°C . For the LECO analysis, fines were produced with a size of $<63 \mu\text{m}$.

Results and Discussion

Overpotential measurements

Comparison of the potential at 1 A cm^{-2} in Table 1 showed a variation of 0-120 mV for repeats of the same material, whilst the potential between different materials was found to vary by an average in the range 140-310 mV. The variation in potential between repeats was possibly due to the inhomogeneous nature of the anode material as only small samples were used. However, as the repeat variation was lower than the differences between materials, the overpotential trends were confirmed and were not experimental error. The order of the materials was also identical to that found in the previous paper [15]; Anode 4 had the lowest potential at 1 A cm^{-2} (and therefore the lowest overpotential), compared to graphite which had the highest potential. Polarisation curves additionally supported this trend, showing the same magnitude differences between anode materials at 1 A cm^{-2} . The polarisation curves also showed that this trend was the same at both lower and higher current densities, and the onset potential for CO_2 production was $\sim 300 \text{ mV}$ lower in Anode 4 than in graphite (Figure 4). LECO measurements of all the melt samples showed little variation in alumina concentration over the course of the experiments, meaning all potential differences could be considered due to the anode materials only. Owing to the fact that all anodes had identical distribution of grain size and pitch type/level, these variations in potential must relate to differences in the coke properties.

Table 1. Potentials of the anodes after 200 seconds at 1 A cm^{-2} . The arrow head direction indicates an overpotential increase.

| Material | Potential at $1 \text{ A cm}^{-2} / \text{V}$ | | | Overpotential |
|----------|---|----------|--------------------|---------------|
| | Repeat 1 | Repeat 2 | Average and ST DEV | |
| Graphite | 1.57 | 1.57 | 1.57 +/- 0.00 | ↑ |
| Anode 1 | 1.45 | 1.40 | 1.43 +/- 0.04 | |
| Anode 2 | 1.39 | 1.38 | 1.38 +/- 0.01 | |
| Anode 3 | 1.30 | 1.37 | 1.34 +/- 0.05 | |
| Anode 4 | 1.20 | 1.32 | 1.26 +/- 0.08 | |

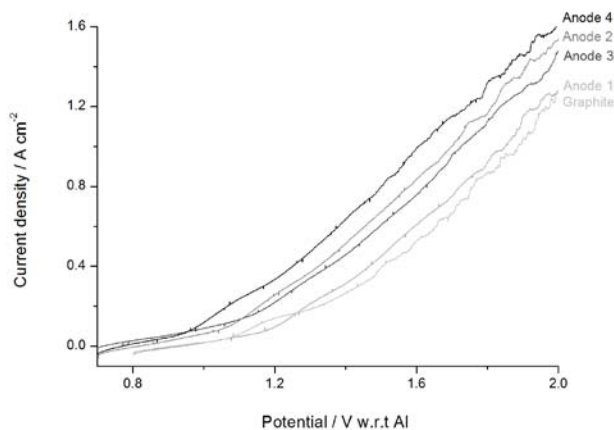


Figure 4. Polarisation curves of graphite and anodes 1 to 4 recorded at 0.1 V s^{-1} . From left to right: Anode 4 (black), Anode 2

(medium grey), Anode 3 (dark grey), Anode 1 (grey) and graphite (light grey). Only forward scans from OCP to 2 V are shown for clarity.

The effect of anode geometry was studied by comparing the new anode design with the defined vertical surface with an unshielded rod with both vertical and horizontal surfaces (Figures 1 and 2). Graphite was the anode material for both designs. When the potential measured over time at 1 A cm^{-2} was compared (Figure 5), there was much less oscillation noise of the potential with the new vertical anode design. It is likely that the noise difference is due to bubbles trapped on the horizontal surface of the unshielded rod [14]; as the bubbles grow in size they cover more of the anode surface causing the potential to increase as local CD increases. When the bubble escapes, the local CD returns to normal and the potential abruptly decreases. The new anode design is therefore superior for measuring overpotential trends.

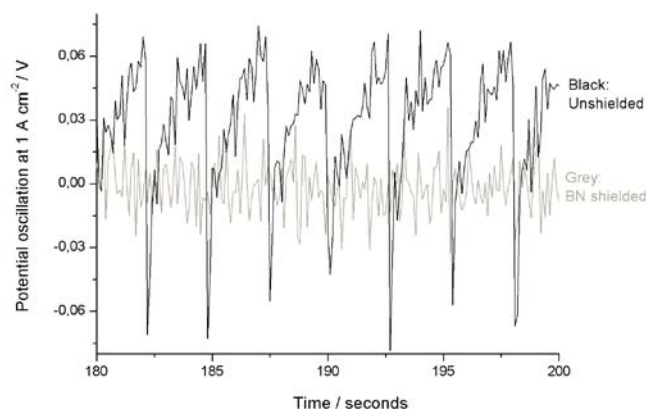


Figure 5. Potential in volts measured at a graphite anode at 1 A cm^{-2} , normalised around zero to show oscillation. Measurements were performed with either the new BN shielding with only a vertical surface (grey), or an unshielded rod with both vertical and horizontal surfaces (black).

Correlations with the overpotential trend

As described in the previous paper, [15], the decreasing overpotential trend correlates well with increasing levels of metals and sulphur. For example, anode 4 had the lowest overpotential and the highest total concentrations of metals and sulphur. As metallic impurities can catalyse air and CO_2 reactivity, it makes sense that these can additionally catalyse the anode reaction and reduce overpotential [1]. However, the chemical properties of an anode are just one possible contributor to the variation in overpotential.

Microstructure was studied by observing polished cut-sections of the anodes under polarised light with optical microscopy, as shown in Figure 6. A clear trend of increasing isotropy was observed from graphite and Anode 1, to Anode 4, as evidenced by a decrease in crystallinity and an increase in fine mosaic structure. The increase in boundaries or 'edges' between crystallites makes it possible that Anodes 3 and 4 have a higher level of electrochemically active sites than anodes 1, 2 and graphite. This

offers another possible explanation of the overpotential differences between the materials.

Another way of characterising the active site content is through the oxygen content of the anodes; as active sites are known to become oxidised [13], measuring the amount of oxygen in a graphitic sample can indicate the relative amount of active sites on the surface. LECO combustion analysis results indicated that increasing levels of oxygen were found from Anodes 1 to 4 (Figure 7). Comparable levels of oxygen were found in each anode and in the corresponding coke used to make it, although the anode had slightly higher oxygen levels than the coke. A reason for this is not clear, but could be due to the added pitch or additional changes to the carbon during anode baking. The oxygen trend found supports the idea that Anodes 3 and 4 could have higher levels of active sites on their surface, but as these anodes also have the highest levels of metallic impurities, the contribution from metal oxides to the total oxygen content measured by LECO cannot be ruled out.

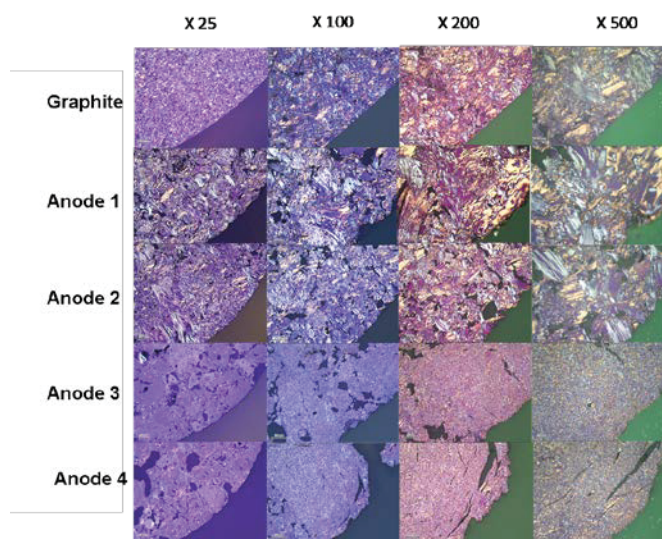


Figure 6. Optical microscopy images (under polarised light) of anodes mounted in epoxy and polished down to 1 µm.

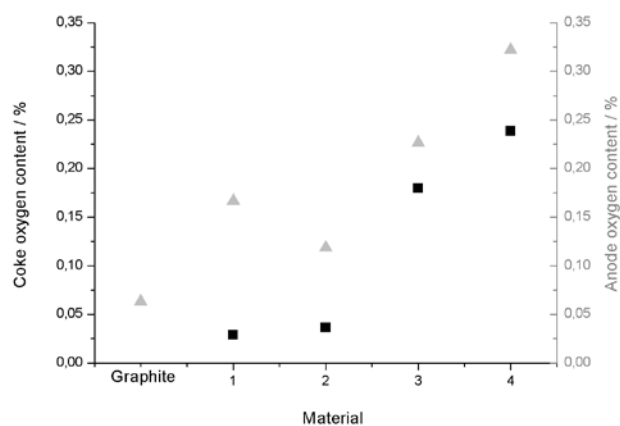


Figure 7. Total oxygen content of the cokes (black squares) and their corresponding anodes (grey triangles). Graphite is also shown for comparison.

The quality of an anode is routinely measured and compared in industry using properties such as air and CO₂ reactivity. The lower the air and CO₂ reactivity, the less consumption and the better performance an anode is expected to have [17]. Analysis results for air and CO₂ reactivity are shown in Table 2. It was shown that Anodes 3 and 4 have the highest air reactivity and low CO₂ reactivity. The fact that Anodes 3 and 4 have the lowest overpotential and the highest air reactivity is interesting; this correlation could make sense if it is assumed that the nature of the electrochemical oxidation of the anode with an oxygen species (i.e. derived from alumina, in the electrochemical reaction), and the thermal oxidation of carbon with oxygen in air is of the same nature.

Table 2. Anode air and CO₂ reactivity.

| Material | Reactivity / mg cm ⁻² h ⁻¹ | |
|----------|--|-------------------|
| | R.Air | R.CO ₂ |
| Graphite | - | - |
| Anode 1 | 39.0 | 19.0 |
| Anode 2 | 29.5 | 5.9 |
| Anode 3 | 69.5 | 7.2 |
| Anode 4 | 70.1 | 7.4 |

The main findings of this paper, including the overpotential trend of the anodes and the correlation of overpotential with other properties studied, are summarised in table 3

Table 3. The relationship of overpotential to impurities, isotropy, oxygen content and air reactivity. The direction of the arrow heads indicates an increase of each property.

| Material | η | Total impurities | Isotropy | O content | R.Air |
|----------|---|------------------|----------|-----------|-------|
| Graphite | ↑ | ↓ | ↓ | ↓ | ↓ |
| Anode 1 | | | | | |
| Anode 2 | | | | | |
| Anode 3 | | | | | |
| Anode 4 | | | | | |

Conclusions

Overpotential was found to vary by as much as 170 mV between four anodes varying only in coke type, confirming the trends found in the previous study [15]. When graphite was also included in the comparison, the variation in potential was 310 mV. The anodes in the current study had no horizontal surfaces; this design was shown to lower the voltage oscillation when compared to unshielded rods with both vertical and horizontal surfaces, most likely due to a reduction in bubble coverage.

Relationships were found between the overpotential trend of the anodes and anode impurity level, isotropy and oxygen content, as summarised in Table 3. Impurities such as metal oxides have been shown in previous literature to act as electrocatalysts and decrease the overpotential of the anode reaction, so this offers one explanation for the trend observed in table 3. However, an alternative explanation for the overpotential trend is the microtexture; increasing isotropy levels and an increase in oxygen

could indicate an increase in active sites on the anode surface from anode 1 to anode 4. Although this is as yet unproven, variations in relative concentrations of electrochemically-active, active sites could also explain the trend in overpotential observed. Overpotential was additionally compared with anode air and CO₂ reactivity; two properties which are routinely used in industry as indicators of anode performance. Overpotential correlated reasonably well with air reactivity. If this relationship is real, it could be that optimising an anode for its electrochemical properties (overpotential) is a trade-off for higher air reactivity.

At present, it is not known whether trace metal impurities or variations in active sites have a dominant effect on overpotential. Additionally, due to the fact that other properties vary between anode types, further important factors towards overpotential could include porosity, surface morphology, real surface area or electrolyte wetting properties, not discussed in this paper.

Acknowledgements

This work was financed by Hydro Aluminium and the Research Council of Norway. Thanks are due to Aksel Alstad at the NTNU workshop where fabrication of experimental parts was required, as well as to Hydro Aluminium lab engineers at Årdalstangen for performing XRF and reactivity (air and CO₂) testing. Additionally, the contributions of Egil Skybakmoen and others at SINTEF are gratefully acknowledged.

References

- Thonstad, J., Fellner, P., Haarberg, G.M., Hives, J., Kvande, H., and Sterten, Å., *Aluminium Electrolysis* 3rd edition ed. 2001, Breuerdruck, Germany: Aluminium-Verlag Marketing & Kommunikation GmbH.
- Leach, C.T., Brooks, D.G., and Gehlbach, R.E., *Correlation of Coke Properties, Anode Properties and Carbon Consumption*. Light Metals, 1997.
- Rolle, J.G. and Hoang, Y.K., *Studies of Vanadium and Sodium on the Air Reactivity of Coke and Anodes*. Light Metals, 1995.
- Kuang, H., Thonstad, J., and Sørli, M., *Effects of Additives on the Electrolytic Consumption of Carbon Anodes in Aluminium Electrolysis*. Carbon, 1995. **33**(10).
- Sørli, M. and Eidet, T., *The Influence of Pitch Impurity Content on Reactivity of Binder Coke in Anodes*, in *Light Metals*. 1998. p. 763-768.
- Feng, N., Zhang, M., Grjotheim, K., and Kvande, H., Carbon, 1991. **29** (1): p. 39-42.
- Liu, Y., Wang, X., Huang, Y., Yang, J.H., and Wang, W., in *Light Metals*. 1995. p. 247-251.
- Haarberg, G.M., Solli, L.N., and Sterten, Å. in *7th Slovak Aluminium Symp.* 1993. Banská Bystrica.
- McClung, M. and Ross, J.A., *A Method to Correlate Raw Material Properties to Baked Anode Core Performance*. Light Metals, 2000.
- Wilkening, S., *Maintaining Consistent Anode Density Using Varying Carbon Raw Materials*. Light Metals, 2009.
- Samanos, B. and Dreyer, C., *Impact of Coke Calcination Level and Anode Baking Temperature on Anode Properties*. Essential Readings in Light Metals: Electrode Technology for Aluminum Production. **4**.
- Banks, C.E., Davies, T.J., Wildgoose, G.G., and Compton, R.G., *Electrocatalysis at graphite and carbon nanotube modified electrodes: edge-plane sites and tube ends are the reactive sites*. Chem. Commun., 2005.
- Laine, N.R., Vastola, F.J., and Walker, P.L.J., *The Importance of Active Surface Area in the Carbon-Oxygen Reaction*. Journal of Physical Chemistry, 1963. **67**.
- Einarsrud, K.E. and Johansen, S.T., *Modelling of bubble behavior in aluminium reduction cells*. Progress in Computational Fluid Dynamics, 2012. **12**(2): p. 119-130.
- Thorne, R.J., Sommerseth, C., Sandnes, E., Kjos, O.S., Aarhaug, T.A., Lossius, L.P., Linga, H., and Ratvik, A.P., *Electrochemical characterization of carbon anode performance*. Light Metals, 2013.
- Kjos, O.S., Aarhaug, T.A., Gudbrandsen, H., Solheim, Å., and Skybakmoen, E., *Fundamental studies of Perfluorocarbon Formation*, in *10 AASTC 2011: Tasmania*.
- Lhuissier, J., Bezamanifary, L., Gendre, M., and Chollier, M.-J., *Use of under calcined coke for the production of low reactivity anodes*. Light Metals, 2009.